

## Corrosion Behavior of Fe-Al-C Alloy

Soekrisno<sup>1</sup> and Ratna Kartikasari<sup>2</sup>

<sup>1</sup>*Department of Mechanical Engineering,  
Faculty of Engineering, Gadjah Mada University, Yogyakarta, Indonesia*

<sup>2</sup>*Nasional College of Technology,  
Department of Mechanical Engineering, Yogyakarta, Indonesia*

### Abstract

Corrosion Behavior of Fe-Al-C alloy with 1.24wt-% Al and 9.05wt-% Al have been studied. The alloys were prepared by an induction furnace under argon atmosphere. The results showed that Al combines with Fe to form FeAl precipitates in 1.24wt-% Al alloy whereas lamellar FeAl<sub>2</sub> was found in 9.05wt-% Al. The results of corrosion test showed that both the alloys are more resistant in NaCl than in H<sub>2</sub>SO<sub>4</sub> solution. There is indication that the form of corrosion is uniform and there is no tendency toward inter granular attack.

**Keywords:** Corrosion Behavior; FeAl Precipitates; Lamellar FeAl<sub>2</sub>; Inter granular attack

### Introduction

Fe-Al-C alloy is a good candidate for replacing some of the conventional stainless steel in several applications at moderate to high temperature<sup>[1]</sup>. Wherein, Al is used to substitute expensive alloy elements in conventional Fe-Cr-C system. Ferritic iron aluminum alloys shows promising physical and mechanical properties along with superior corrosion and oxidation resistance at much lower raw material cost<sup>[2]</sup>.

Fe-Al alloys exhibit poor toughness. These are brittle at room temperature<sup>[3]</sup>. Addition of carbon to Fe-Al containing 8.5 to 16 wt-% Al gives higher strength<sup>[4]</sup>, and better machinability<sup>[5]</sup>. It has been shown that low carbon content (0.05 and 0.1 wt-%) in Fe-9 wt-% Al leads to low tensile ductility<sup>[6]</sup>. Whereas, the ESR (Electro Slag Refined) ingots of Fe-10.5Al and Fe-13Al alloys containing high (0.5 and 1.0 wt-%) carbon exhibit excellent hot workability<sup>[7]</sup>.

Fe-Al-C alloy is being developed for elevated temperature structural application up to 873K<sup>[8]</sup>.

Aluminum plays a major role in the oxidation and corrosion resistance which is characteristic of the binary Fe-Al alloy<sup>[9]</sup>. The Fe-Al-C alloys have good corrosion resistance in a neutral environment. Its corrosion rates are comparable to that of white cast-iron in acid environments<sup>[10]</sup>. However, few data are available on the corrosion phenomena of Fe-Al alloy in acid media like H<sub>2</sub>SO<sub>4</sub>.

In this Study, Corrosion Behavior of Fe-9Al-0.6C alloy have been Reported.

### Experimental Procedure

Thirty five kilograms of Fe-Al-C was prepared from mild steel scrap, high purity aluminum, and Mn with medium C. The alloy was prepared in an induction furnace under argon atmosphere. The chemical compositions are listed in Table 1. The ingot was cut using bimetallic band saw blade to make specimens for corrosion (14 mm in gauge diameter and 3 mm in gauge length) studies. The surface of the corrosion specimens were mechanically polished with abrasive paper up to 1200 grit, after surface finishing. The last mechanical polishing was done with 0.5  $\mu$ m alumina paste. The corrosion measurements were carried out with three-electrode polarization in 0.5% NaCl and 0.05M H<sub>2</sub>SO<sub>4</sub>. The corrosion type and the morphology of the oxide scale were determined by optical and scanning electron microscopes (SEM). Corrosions products were examined using EDS/EDAX.

The polished section were subsequently etched with 3.3% HNO<sub>3</sub>-3.3% CH<sub>3</sub>COOH-0.1% HF-93.3% H<sub>2</sub>O by volume for micro structural examination by optical microscope.

**Table 1:** Chemical Composition (wt-%) of the Alloys Tested

Alloys	Al	C	Mn	Si	P	S	Fe
A	1.24	0.55	0.02	0.02	0.03	0.02	Bal.
B	9.05	0.6	0.66	0.18	0.03	0.02	Bal.


### Results and Discussion

The Three-electrode polarization technique was used to measure corrosion rate of the alloy. The results are shown in table 2.

**Table 2:** Corrosion Rate of the Fe-Al-C Alloy


Specimen	I corr( $\mu$ A/cm <sup>2</sup> )		R (mpy)	
	0.5% NaCl	0.5% H <sub>2</sub> SO <sub>4</sub>	0.5% NaCl	0.05 M H <sub>2</sub> SO <sub>4</sub>
Fe-1.24Al-0.55C	11.25	37.47	0.37	1.81
Fe-9.05Al-0.6C	8.96	21.62	0.35	0.74

Table 2 indicates that not only in the 0.5% NaCl but also in the 0.05 M  $H_2SO_4$  solution, the corrosion rate of Fe-1.24Al-0.55C alloy is greater than that of Fe-9.05Al-0.6C alloy. The difference of the corrosion rate is 15.99% and 59.35% respectively. This is primarily because of higher Aluminum content. A protective passive film was formed on the specimen surface at the stabilized corrosion potential. Figs 1 to 3, indicate that the oxide layer is rich in aluminum. The X-ray diffraction results show that the outer region is  $Al_2O_3$ . These corrosion rates are in either excellent or good category<sup>[11]</sup>.

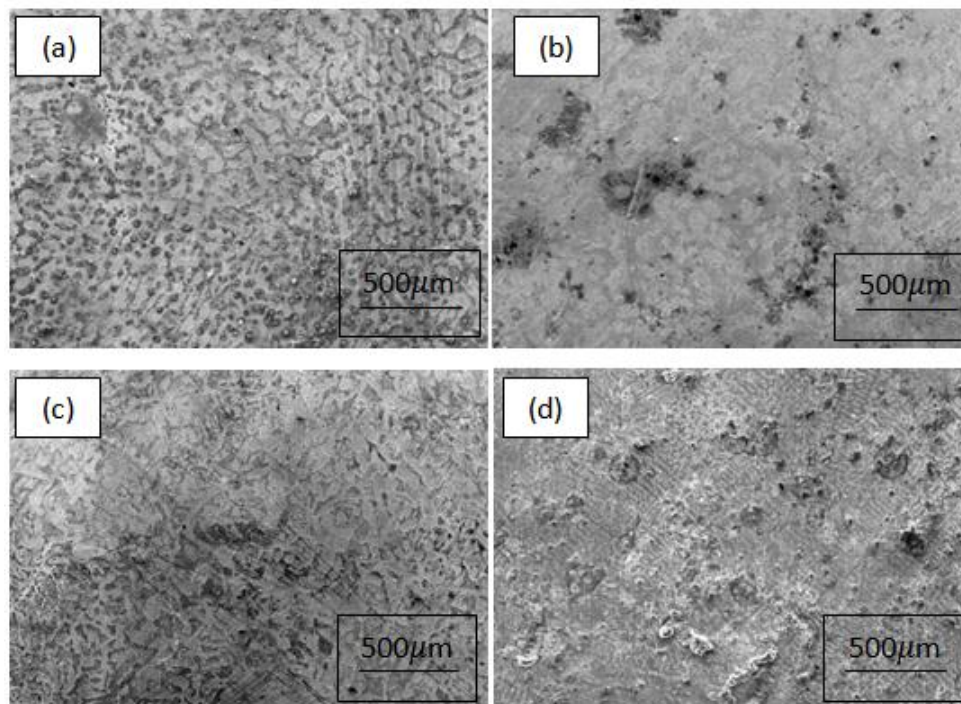


**Figure 1:** SEM Micrographs of as cast Fe-Al-C Alloy after Corrosion (a). Fe-1.24Al-0.55C in 0.05 M  $H_2SO_4$  (b). Fe-1.24Al-0.55C in 0.5% NaCl c. Fe-9.05Al-0.6C in 0.05 M  $H_2SO_4$  d. Fe-9.05Al-0.6C in 0.5% NaCl


Fig 1. shows surface corroded for the alloys. Light and dark pattern microstructures seem at 1.2% Al. whereas, in the higher magnification (Fig.3) oxide pattern was very clear. SEM-EDS analysis (Fig 4-5) shows present some oxides like  $Al_2O_3$  and FeO that are come from composition of these alloy, while  $Na_2O$ ,  $SO_3$  and Cl are from corrosion medium. The micrograph cross section of as cast Fe-Al-C alloy after corroded show that the oxide layers formed on the surface of the alloy after corrosion testing (Fig 2). It was observed that thin oxide layer formed on the surface but internal oxidation product could not be observed. The thickness of oxide layer of Fe-1.26Al-1.05C alloy could be observed in both of corrosion medium but in the Fe-9Al-0.6C alloy couldn't. These phenomena connected with corrosion rate. No inter granular attack could be observed in these conditions.

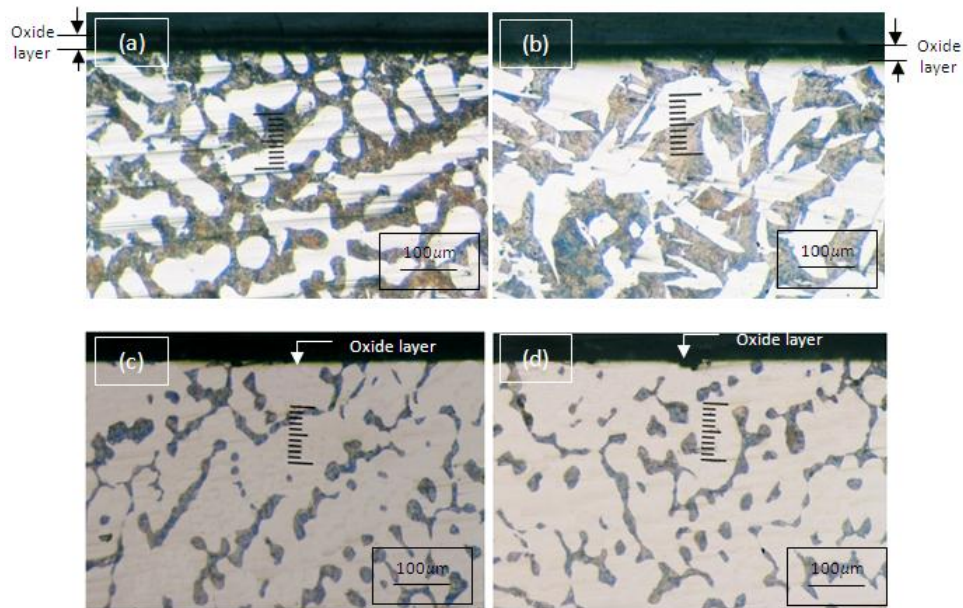


**Figure 2:** Metallographic cross section of as cast Fe-Al-C alloy after corrosion (a). Fe-1.24Al-0.55C in 0.05 M  $H_2SO_4$  (b). Fe-1.24Al-0.55C in 0.5% NaCl c. Fe-9.05Al-0.6C in 0.05 M  $H_2SO_4$ d. Fe-9.05Al-0.6C in 0.5% NaCl

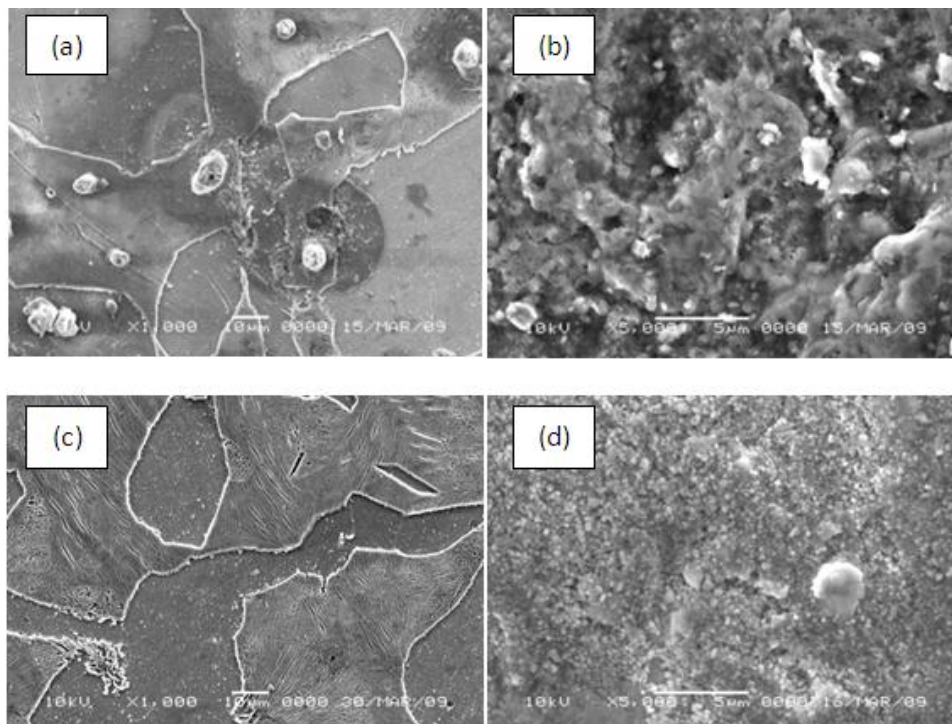

**Figure 3:** SEM micrographs high magnification of as cast Fe-Al-C alloy after corrosion (a). Fe-1.24Al-0.55C in 0.05 M  $H_2SO_4$  (b). Fe-1.24Al-0.55C in NaCl c. Fe-9.05Al-0.6C in 0.05 M  $H_2SO_4$  d. Fe-9.05Al-0.6C in NaCl

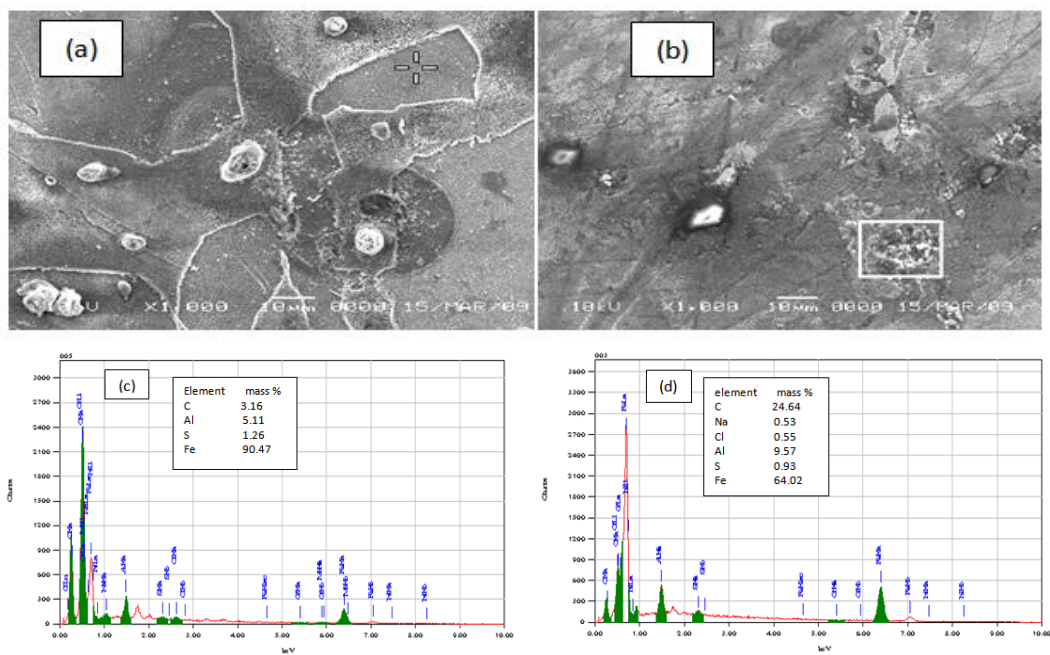

**Figure 4:** SEM micrographs of as cast of Fe-1.24Al-0.55C alloy after corroded (a). SE image in 0.05M H<sub>2</sub>SO<sub>4</sub> 0.05M (b). SE image in 0.5% NaCl. EDS result in 0.05M H<sub>2</sub>SO<sub>4</sub> 0.05M (c). EDS result in 0.5% NaCl (d).

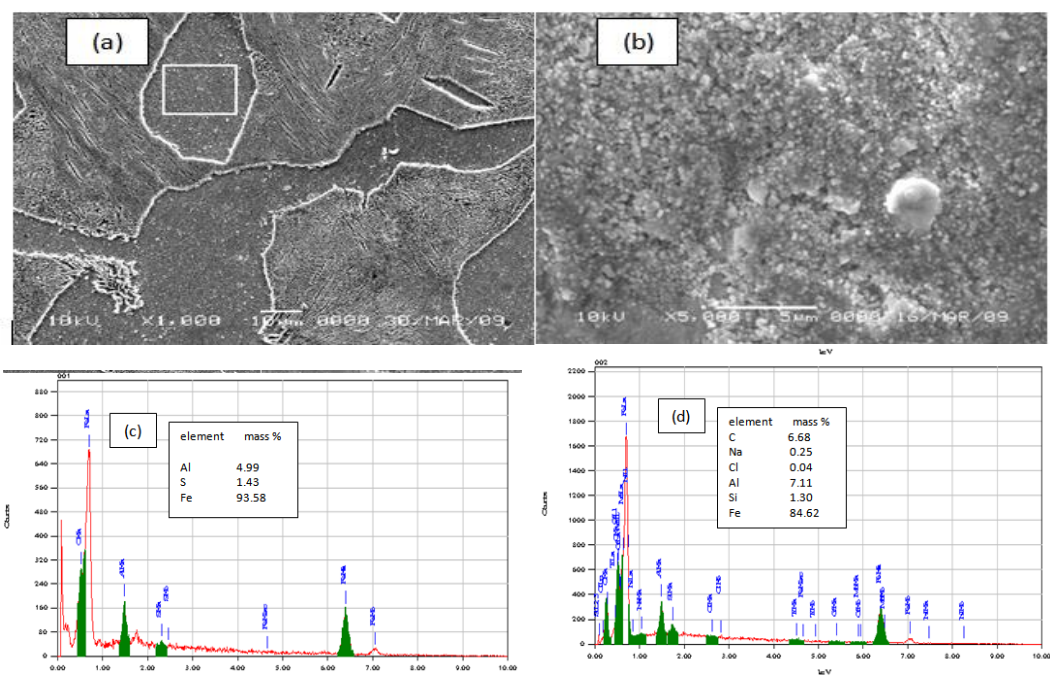

**Figure 5:** SEM Micrographs of as Cast of Fe-9.05Al-0.6C alloy after Corroded (a). SE image in 0.05M H<sub>2</sub>SO<sub>4</sub> 0.05M (b). SE image in 0.5% NaCl. EDS Result in 0.05M H<sub>2</sub>SO<sub>4</sub> 0.05M (c). EDS result in 0.5% NaCl (d).

## Conclusions

The Fe-1.24Al-0.55C has uniformly distributed white colored Fe-Al precipitates on the darker matrix while the Fe-9.05Al-0.6C alloy has lamellar white colored Fe-Al<sub>2</sub> among a dark iron-aluminum carbide particle. General corrosion could be observed after three-electrode polarization but there is no trend toward to inter granular corrosion attack.

## References

- [1] Huang, Y.D., and Froyen, L., 2006, Recovery, Recrystallization, and Grain Growth in Fe<sub>3</sub>Al Based alloys, *Intermetallics*, Vol. 10, 443.
- [2] Kobayashi, S., Zaefferer, S., Schneider, A., Raabe, D., and Frommeyer, G., Optimisation of Precipitation for Controlling Recrystallization of Wrought Fe<sub>3</sub>Al Based Alloys, *Intermetallics*, 2005, 13, 1296-1303.
- [3] Jablonska M, Rodak K, and Niewielski G, 2006, Characterization of The Microstructure of FeAl alloy after Hot Deformation, *Journal of Achievements in Materials and Manufacturing Engineering*, Vol. 18, Issue 1, 107-110.
- [4] Baligheid RG, Prakash U, Ramakrishna Rao V, Rao PK, and Ballal NB, 1996, Effect of Carbon Content on Mechanical Properties of Electroslag Remelted Fe<sub>3</sub>Al Based Intermetallic alloys, *ISIJ*, Vol. 36, No. 12, 1453-1458.
- [5] Baligheid RG, Prakash U, and Radha Krishna, 1998, Effect of Carbon Addition on Structure and Mechanical Properties of Electroslag Remelted Fe-20wt.%Al alloy, *Materials Science and Engineering A*, Vol. 249, No. 1-2, 97-102.
- [6] Stolof NS and Liu CT, 1994, Review: Environmental embrittlement of Iron Aluminides, *Intermetallics*, 2, pp. 75-87.
- [7] Baligheid RG and Satya Prasad K, 2007, Effect of Al and C on Structure and Mechanical Properties of Fe-Al-C alloys, *Mater. Sci. Technol.*, 23, No.1, 38-44.
- [8] Sikka VK, Viswanathan S, and McKamey CG, 1993, in 'Structural Intermetallic', (ed. R. Darolia et al.), Warrendale, PA, TMS. pp. 483-491
- [9] Kao CH, and Wan CM, 1988, Effect of Temperature on the Oxidation of Fe-7.5Al-0.65C alloy, *J. Mater. Sci.*, 23, 1943-1947.
- [10] Giza K, Bala, H, Wysocki JJ, and Szymura S, 1998, Corrosion Resistance of the Fe-Al-C Permanent Magnet Alloy, *Intermetallics*, Vol 6, issue 5, 357-362.
- [11] Fontana GM, 1987, *Corrosion Engineering*, 3th ed., McGraw Hill Inc. Singapore, pp 153-181