

# Utilization of Wood Chemical Production Waste in Wood Composite Materials Technology

<sup>1</sup>Plotnikov Nikolay Pavlovich and <sup>2</sup>Plotnikova Galina Pavlovna

<sup>1</sup>Dozent, Bratsk State University, St. Makarenko 40, Bratsk, Russia.  
Orcid: 0000-0001-9729-0806

<sup>2</sup>Dozent, Bratsk State University, St. Makarenko 40, Bratsk, Russia.  
Orcid: 0000-0002-7436-3037

## Abstract

At the present stage of scientific and technological development, the economy and rational use of material resources is becoming the main condition for increasing the efficiency of social production. The problem of improving the environmental safety of the waste management system of chemical processing of biomass of wood is quite acute in every forest producing and timber processing region. According to expert estimates, the annual volume of waste generated by the hydrolysis and wood chemical industry is 2-5-106 tons, and the accumulated volume in the country exceeds 9-10-10 tons. The main share in the total waste of these industries is occupied by hydrolytic lignin, organic slurry, inorganic gypsum-based sludge, pine nut shells and pyrolytic resins. Study of the possibility of using to investigate hydrolytic lignin as a modifier of phenol-formaldehyde resin for the production of plywood have been conducted. Mathematical models of the process of pressing glued plywood were developed and the optimal parameters for the production of plywood were determined based on the use of SFZh-3013 resin modified with hydrolytic lignin.

**Keywords:** hydrolysis lignin, modification, phenol-formaldehyde resin, quality, strength, physical and mechanical indicators.

## INTRODUCTION

One of the directions of processing plant materials is the use of acid hydrolysis of woody biomass, which historically has been directed to the use of the carbohydrate part, to produce ethanol. During the hydrolysis of wood waste is formed - technical hydrolytic lignin (THL). To date, the enterprises have accumulated many millions of tons of hydrolytic lignin. [1]. Lignin, along with cellulose and protein substances, is one of the most common natural polymers, which in itself determines the significance of research aimed at understanding its nature and behavior in chemical reactions. Currently in the woodworking industry, liquid hot-cured resole resins are used. However, the high cost and scarcity of phenol significantly increases the cost of products based on these resins - the proportion of binder in the cost of laminated wood is up to 40%. Thus, the use of technical lignins for the production of low molecular weight phenolic compounds will reduce the cost of production products using phenol, such as, for example, the

production of binding resins for the production of plywood, fiberboard. [2-3]. The aim of the work is the development of technological modes of production of glued plywood with improved physico-mechanical parameters based on the use of phenol-formaldehyde resins modified with lignin hydrolyzed.

## MATERIALS AND METHODS

The work was carried out on peeled veneer samples made of pine wood on a fiberboard. Studies to determine the physicochemical parameters of modified resins were carried out in accordance with GOST 20907 "Phenol-formaldehyde resins". Studies to determine the wetting ability of modified resins were performed using an MIS-11 microscope. The gluing of plywood with the format of 0.4 mx 0.4 m was carried out in a laboratory press of the brand OKS 1671M according to the following technological parameters: humidity of pine veneer -  $6 \pm 2\%$ ; glue consumption - 120 g / m<sup>2</sup>; plywood thickness - 12 mm; layer pack 5; package assembly and holding time before gluing - 10 min; gluing in one gap of the press - 1 sheet each; aging after gluing - no less than 24 hours. The physicomechanical parameters of the finished product were determined according to GOST 3916.2-96 "General-purpose plywood with outer layers of softwood veneer". [4-5]. The obtained experimental data of one-and multi-factor experiments were processed by the methods of mathematical statistics.


### Used materials:

- phenol-formaldehyde resin SFZh-3013;
- technical hydrolyzed lignin.

According to the statements of numerous authors [Doronin Yu. G., Kodratyev V.P., Anokhin A.E., Bokov A.N. et al.] adhesion of adhesive joints largely depends on the processes of wetting and spreading of the adhesive, the evaluation of which is the wetting ability of the surfaces of the glued veneer [6-7]. Therefore, at the first stage of the research, the determination of wetting ability was assumed, the criterion of which is the wetting angle. The measurement of the wetting angle of the modified adhesive compositions was carried out on samples of peeled veneer made from pine wood, as well as on a substrate of hardboard using a microscope MIS-11. [8].


## RESULTS

The results of studies of the dependence of the wetting angle on a peeled veneer substrate and a fibreboard substrate on the amount of hydrolyzed lignin added to a SFG-3013 phenol-formaldehyde resin resin are presented in the form of graphical dependencies in fig.1.

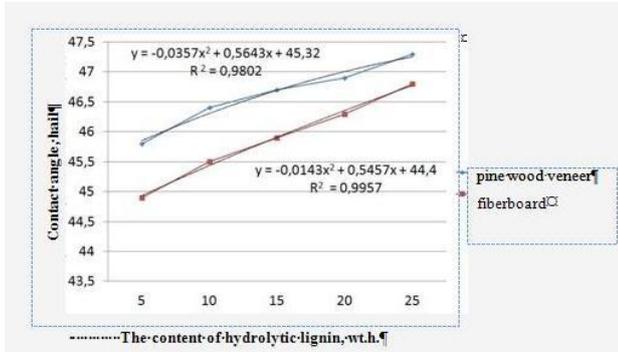

**Fig 1** Schedule of dependence of the average values of the wetting angle

From the presented graphical dependence, we can draw the following conclusion that the wetting ability of the pine veneer substrate is worse than fiberboard. With an increase in the input of hydrolytic lignin, the wetting angle increases, therefore, the wetting ability deteriorates. Surface tension is directly related to the work of adhesion. Interfacial interaction, or interaction between the surfaces of condensed bodies brought into contact of different natures, is called adhesion (adhesion). The work of adhesion  $W_a$ , characterizing the strength of the adhesive bond, is determined through the cosine of the wetting angle and surface tension. According to the data obtained, the dependence of the work of adhesion on the amount of hydrolyzed lignin in the adhesive composition, shown in Fig. 2

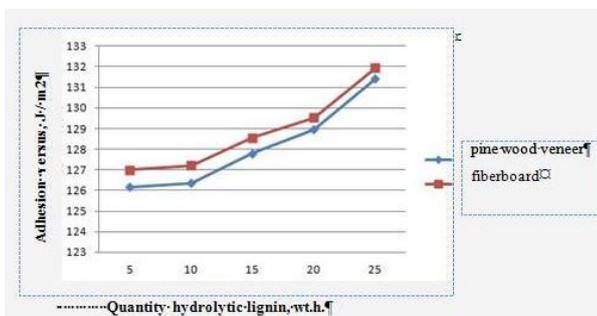

**Fig. 2.** Schedule of adhesion versus input quantity hydrolytic lignin in the adhesive composition

From the presented graphical dependence we can draw the following conclusion: with an increase in the amount of hydrolyzed lignin introduced into the composition, the work of adhesion increases. Adding 5-10 parts by weight of hydrolytic lignin does not significantly increase adhesion. With further increase in the number of injected hydrolytic lignin, the work of adhesion increases dramatically. Using the obtained results of preliminary experiments, in laboratory conditions at the Department of Reproduction and processing of forest resources of the Bratsk State University, studies on gluing veneer were carried out and studying the strength properties of the materials obtained. The variable factors of research and the intervals of

their variation are given in table 1.

**Table 1** - Main factors and levels of their variation

Name of the factor	Designation	Lower level	Basic level	Upper level	Variation interval
Amount of hydrolytic lignin, wt.h.	$X_1$	5	10	15	5
Pressing pressure, $P$ , MPa	$X_2$	1.4	1.6	1.8	0.2
Pressing cycle duration, $\tau_1$ , min	$X_3$	9	10	11	1
Pressing temperature, $t$ , °C	$X_4$	115	125	135	10

Mathematical description of the dependence of the tensile strength of plywood for bending:

$$Y_1 = 42.63 - 0.97 \cdot \tilde{O}_1 + 1.73 \cdot \tilde{O}_3 - 6.33 \cdot X_2^2 + 6.03 \cdot X_4^2 + 0.375 \cdot X_1 \cdot X_2$$

Mathematical description of the dependence of the strength of glued plywood on chipping on the adhesive layer:

- in dry form:


$$Y_2 = 2.02 - 0.102 \cdot \tilde{O}_1 + 0.036 \cdot \tilde{O}_4 + 0.21 \cdot X_1 \cdot X_4 - 0.09 \cdot X_2^2$$

- after boiling

$$Y_3 = 1.265 - 0.064 \cdot \tilde{O}_1 - 0.261 \cdot \tilde{O}_4 - 0.012 \cdot X_1 \cdot X_4 + 0.15 \cdot \tilde{O}_2^2 - 0.3 \cdot X_1^2 + 0.115 \cdot X_3^2 + 0.15 \cdot X_4^2$$


At the next stage, a multifactorial experiment was conducted in order to obtain an adequate mathematical description of the technological production of plywood.

Based on the obtained research results, mathematical models were developed for describing the research process, which allow predicting the strength characteristics of the plywood produced with a given probability. According to the obtained regression equations, graphical dependences in the form of response surfaces are constructed. The dependence of the strength of plywood when it is spalled over the adhesive layer after boiling for 1 hour is shown in Fig. 3.

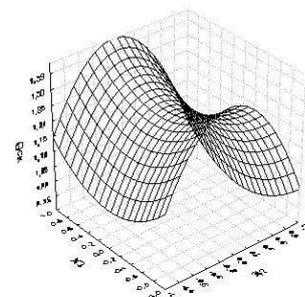

**Fig 3** Dependence of the strength of plywood when it is spalled over the adhesive layer after boiling for 1 hour

The dependence of the strength of plywood during static bending on the number of injected hydrolytic lignin in the composition and pressing pressure is shown in Fig. 4.

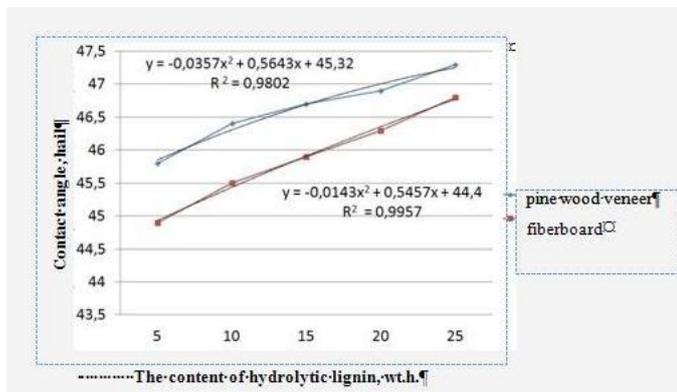

**Fig 4** Schedule of dependence of the average values of the wetting angle.JPG

## DISCUSSION

From the presented graphical dependence, we can conclude that the maximum strength of plywood samples on the basis of SFZh-3013 modified with hydrolytic lignin on the adhesive layer after boiling for 1 hour is observed during the pressing cycle of 10 minutes, pressing temperature 135 °C, pressing pressure 1.6 MPa, when the content of hydrolytic lignin 10 wt.h.

From the presented graphical dependence, it can be concluded that the maximum maximum tensile strength of plywood samples based on SFG-3013 modified with hydrolytic lignin during static bending is observed at a pressing temperature of 135 °C, a pressing cycle of 10 minutes, a pressing pressure of 1.8 MPa, and a content of hydrolytic lignin 5- 10 wt.h.

## CONCLUSIONS:

1. Thus, after analyzing the schedules of the effects of factors and their interactions, it can be concluded that the optimal mode of pressing is: the amount of injected hydrolytic lignin in the SFZh-3013 resin grade is 5-10 parts by weight; pressing pressure 1.6 MPa, pressing temperature 135 °C and pressing time 9-10 minutes
2. The introduction of regimes developed using regression equations, with a sufficient degree of accuracy describing the pressing process, will significantly improve the efficiency of plywood production by saving energy and material costs and preserving product quality.

## REFERENCES

1. G.P., Plotnikova, . Plotnikov N.P., and Kuzminih E.A. 2013. *The use of hydrolytic lignin in the production of wood-polymer composites.*
2. G.P., Plotnikova, and . Plotnikov N.P. 2013. *Modification of paraffin emulsions for the production of chipboard.*
3. —. 2013. *Modification of the binder for the use of substandard raw materials in the production of chipboard.*
4. —. 2013. *Optimization of the production process of chipboard on a modified binder with the use of substandard raw materials.*
5. N.P., Plotnikov, and Plotnikova G.P. 2013. *Improvment of the production technology of wood-based materialsH.*
6. —. 2013. *Investigation of the rheological properties of modified adhesive compositions.*
7. Plotnikov, N. P., and G. P. Plotnikova. 2014. *Structure of naphthol modified ureaformaldehyde resins by using the method of nuclear magnetic resonance.*
8. Plotnikov, N.P., G.P. Plotnikova, and S.H. 2015. *Simonyan Modeling of technological process of wood composite material production of woodworking and wood chemical complex wastes.*